

International Federation for Heat Treatment and Surface Engineering – IFHTSE

5th International Conference on Quenching and Control of Distortion

A3TS-AWT-ASTT-SVW-VWT

European Conference on Heat Treatment 2007

Berlin, April 25 – 27, 2007

# Modelling Phase Transformations and Material Properties Critical to Prediction of Distortion during Heat Treatment of Steels

Zhanli Guo\*, Nigel Saunders, Peter Miodownik, Jean-Philippe Schillé

*Sente Software Ltd., Surrey Technology Centre, Guildford GU2 7YG, U.K.*

\* [z.guo@sentesoftware.co.uk](mailto:z.guo@sentesoftware.co.uk)

## Abstract

This paper describes the recent development of models in computer software JMatPro for the calculation of phase transformations and material properties critical to the prediction of distortion during heat treatment of steels. The success of these models is based on accurate description of all the major phase transformations taking place including the formation of ferrite, pearlite, bainite and martensite, as well as calculation of the properties of different phases formed during the heat treatment process. One advantage of the current models is that they can be applied to many types of steels including medium to high alloy types. A wide range of properties such as density, thermal expansion coefficient, thermal conductivity, strength and hardness can be calculated, all as a function of time, temperature, and cooling rate, even for arbitrary cooling profile. The material data calculated from JMatPro have been exported directly to FE/FD-based packages for forging/deformation simulation.

## Keywords

Material properties, modelling, distortion, TTT diagram, Jominy hardenability, heat treatment

## 1 Introduction

Unwanted distortion generated during heat treatment is a major industrial problem because it critically affects the dimensional accuracy of precision components. If distortion can be predicted and controlled, then corrections can be made during the earlier machining stage so that the components reach their final desired shape and dimension after heat treatment.

Prediction of distortion induced by heat treatment has generally been based on prior experience or by a trial and error approach. In recent years, with the significant improvement of computing power, finite-element/finite-difference (FE/FD) simulation tools have been developed to tackle this problem. While being successful in some cases, almost all of the FE/FD packages suffer from one common problem: the lack of accurate material property data. This is because the prediction of distortion requires detailed knowledge of the material properties of each phase

Arbeitsgemeinschaft Wärmebehandlung und Werkstofftechnik –AWT

Prof. Dr.-Ing J. Grosch FASM · Chairman 5QCD2007

TU Berlin · FG Werkstofftechnik · EB13· Strasse des 17. Juni 135 · D-10623 Berlin

Phone xx49-30-314-22372· e-mail: [Johann.Grosch@tu-berlin.de](mailto:Johann.Grosch@tu-berlin.de)

**International Federation for Heat Treatment and Surface Engineering – IFHTSE**  
**5th International Conference on Quenching and Control of Distortion**

**A3TS-AWT-ASTT-SVW-VWT**  
**European Conference on Heat Treatment 2007**

**Berlin, April 25 – 27, 2007**

formed during heat treatment, all of which are a function of alloy composition, heat treatment procedures (microstructure) and temperature. The following information on materials properties has to be known for distortion prediction:

- Phase transformation kinetics, i.e. TTT and CCT diagrams.
- Temperature dependent thermophysical properties of each phase formed, such as density, Young's modulus, thermal expansion coefficient, and thermal conductivity.
- Temperature dependent mechanical properties of each phase formed, including tensile strength, yield strength and hardness.

In the present paper, the development of a computer program, JMatPro (**Java-based Materials Property simulation software**), is reported which can calculate the above material properties for general steels. The success of the program is based on an accurate description of all the major phase transformations taking place during heat treatment [Saunders, 2004], as well as an accurate calculation of the properties of different phases formed in steels. **This paper is a natural extension of our previous work [Guo, 2005], where model development was explained in details and extensive validation had been carried out.** Consequently the present paper will focus on a **specific** application of JMatPro, which generates material data that otherwise has to be measured through experiments such as: dilatometry, Jominy hardenability test, and Gleeble<sup>®</sup> testing.

## 2 Modelling of Material Data for Distortion Prediction

### 2.1 TTT and CCT Diagrams

Significant work has been carried out over recent decades to develop models that can calculate TTT/CCT diagrams for steels [Kirkaldy, 1982 and 1984; Bhadeshia, 1981 and 1982; Lee, 1993]. Although successful for low alloy steels, these models are limited when it comes to more highly alloyed types. This problem has been solved in the most recent version of JMatPro, which is now able to calculate TTT/CCT diagrams for steels of all types, including the highly alloyed ones [Guo, 2005; Saunders, 2004].

Two new features in the models deserve special attention. One is the determination of the austenite composition at the quenching temperature. When carbides or other second phases are present at this temperature, it would be inappropriate to use the overall alloy composition as the composition of the austenite to be decomposed. In the present treatment, the composition of the austenite present at the quenching is always calculated directly [Li, 2002] and then used in the subsequent modelling. The other feature is that the formation of martensite and bainite is affected by the prior formation of ferrite. The carbon rejected by the formation of ferrite is then incorporated into the remaining austenite, which may have a significant impact on further transformations. For example, increased carbon in austenite reduces bainite and martensite start temperatures and increases the strength of the transformed phases.

Arbeitsgemeinschaft Wärmebehandlung und Werkstofftechnik –AWT

Prof. Dr.-Ing J. Grosch FASM · Chairman 5QCD2007

TU Berlin · FG Werkstofftechnik · EB13· Strasse des 17. Juni 135 · D-10623 Berlin

Phone xx49-30-314-22372· e-mail: [Johann.Grosch@tu-berlin.de](mailto:Johann.Grosch@tu-berlin.de)

**International Federation for Heat Treatment and Surface Engineering – IFHTSE**  
**5th International Conference on Quenching and Control of Distortion**

**A3TS-AWT-ASTT-SVW-VWT**  
**European Conference on Heat Treatment 2007**

**Berlin, April 25 – 27, 2007**

## 2.2 Thermophysical and Physical Properties

Thermophysical and physical properties are critical parameters for the prediction of distortion induced by heat treatments or processing. JMatPro's ability to model these properties has been well documented in previous published work for various metallic systems [Sente Software, 2005; Guo, 2005]. The relevant properties that can be modelled include: density, molar volume, thermal expansion coefficient, Young's, bulk and shear moduli, Poisson's ratio, thermal conductivity and diffusivity, electrical conductivity and resistivity, all are provided for each phase present when necessary.

## 2.3 Mechanical Properties During Heat Treatment

A heat treatment cycle typically includes heating, isothermal holding and cooling procedures. The mechanical properties, as well as physical and thermophysical properties, of steels during those procedures can now be calculated [Sente Software, 2005; Guo, 2005]. The microstructure is assumed to be "frozen" when below the final heat treatment temperature, and reach equilibrium when above this temperature. The calculation of mechanical properties during isothermal holding or cooling has been demonstrated previously [Guo, 2005].

# 3 Applications

## 3.1 Cooling Rate on Phase Transformations and Material Properties

An example is given to demonstrate how cooling rate affects the phase transformations during quenching. The alloy is a 4140 steel, with composition (wt%): Fe-0.98Cr-0.77Mn-0.21Mo-0.04Ni-0.15Si-0.37C, and grain size ASTM 7~8. Figure 1 shows the evolution of various phases during cooling at 20°C/s and 5°C/s, respectively. A significant amount of martensite is formed during cooling at 20°C/s, but much less at 5°C/s. Cooling at 5°C/s results in about 4% and 6% ferrite formed before the start of bainite (Bs) and martensite (Ms) formation, respectively. The change of carbon concentration in the remaining austenite caused by the formation of such small amount of ferrite is enough to lower the Bs and Ms temperatures by 10°C.

The cooling rate effect on physical and mechanical properties has been shown here, again using steel 4140 as an example. Five cooling rates are used: 100, 10, 1, 0.1, and 0.01 °C/s respectively. Typical material properties relevant to the prediction of distortion such as density, linear expansion coefficient, thermal conductivity and yield stress at different cooling rates are plotted in Figure 2. The properties at 100°C/s and 10°C/s are very close, since the amount of martensite is over 90% in both cases.

Arbeitsgemeinschaft Wärmebehandlung und Werkstofftechnik –AWT

Prof. Dr.-Ing J. Grosch FASM · Chairman 5QCD2007

TU Berlin · FG Werkstofftechnik · EB13 · Strasse des 17. Juni 135 · D-10623 Berlin

Phone xx49-30-314-22372 · e-mail: [Johann.Grosch@tu-berlin.de](mailto:Johann.Grosch@tu-berlin.de)

Berlin, April 25 – 27, 2007

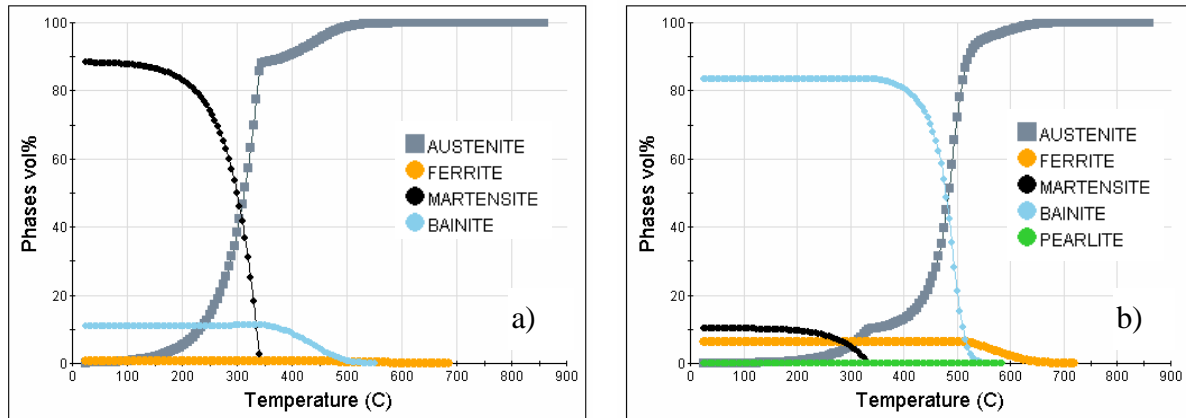


Figure 1. Microstructure evolution in a 4140 steel during cooling at (a) 20°C/s and (b) 5°C/s

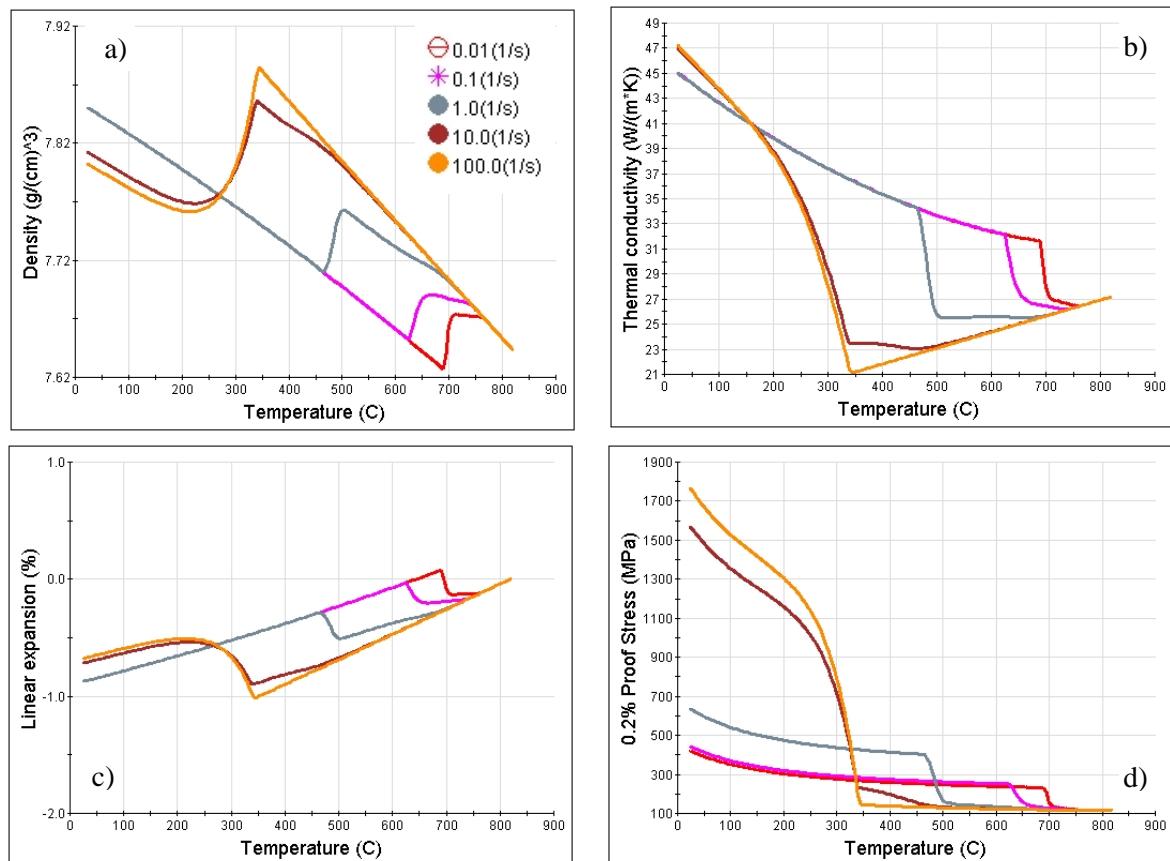


Figure 2. Properties calculated for a 4140 steel at cooling rates from 0.01 to 100 °C/s, a) density, b) thermal conductivity, c) linear expansion, and d) proof stress

Arbeitsgemeinschaft Wärmebehandlung und Werkstofftechnik –AWT

Prof. Dr.-Ing J. Grosch FASM · Chairman 5QCD2007

TU Berlin · FG Werkstofftechnik · EB13· Strasse des 17. Juni 135 · D-10623 Berlin

Phone xx49-30-314-22372· e-mail: [Johann.Grosch@tu-berlin.de](mailto:Johann.Grosch@tu-berlin.de)

**Berlin, April 25 – 27, 2007**

### 3.2 Complicated Cooling Profile: Jominy Hardenability Test

The major steps for predicting Jominy hardness using this model are explained below. One has to calculate the microstructure evolution (final microstructure) and hardness for each position along the Jominy bar.

Each position along the Jominy bar is associated with a complex cooling pattern. Kirkaldy et al. established a formula to calculate the cooling curve for each position [Kirkaldy, 1978 and 1984]. The calculated curve is in fairly good agreement with curves calculated from other analytic or finite-element methods [Li, 1998]. Figure 3 shows the cooling curves for three positions along the Jominy bar, i.e. 0.25, 1.25 and 2.5 inches from the quenching end.

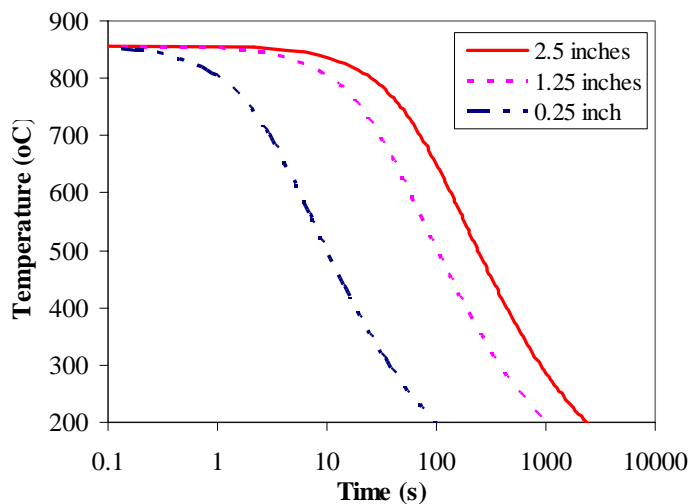


Figure 3. Cooling curves for three positions from quenching end on a Jominy bar

The model applied in JMatPro allows one to input user-defined cooling profiles, for instance those shown in Figure 3. The basic idea is to treat such cooling curves as a series of isothermal steps, each with different holding time. The microstructure evolution during cooling at each position can then be calculated, and the final microstructure is used to calculate the Jominy hardness. Two alloys were used as examples here, one is the 4140 steel (same as in 3.1), and the other is a 5140 steel (Fe-0.42C-0.93Cr-0.68Mn-0.16Si, grain size ASTM 6.5). The microstructure change along the Jominy bar for the two alloys is shown in Figure 4.

The hardness can be readily calculated when the microstructure at room temperature is known. The Jominy hardenability curve was calculated and compared with the experimental curve [ASM, 1977] for the two alloys in Figure 5. Good agreement was achieved for both alloys. It should be noted that the Jominy curve of alloy 5140, Figure 5(b), exhibits two zones: a fast hardness drop from the quenching end to 0.75 inch depth, and a slow hardness drop between 0.75 and 2.5 inches. This behaviour can be readily explained by the microstructure change along the Jominy quench bar shown in Figure 4(b). The initial fast drop in hardness is mainly due to the formation of bainite at the expense of martensite. At positions over 0.75 inch in depth, pearlite starts to form at the expense of bainite (the stronger of the two phases), which leads to the second slow drop in hardness.

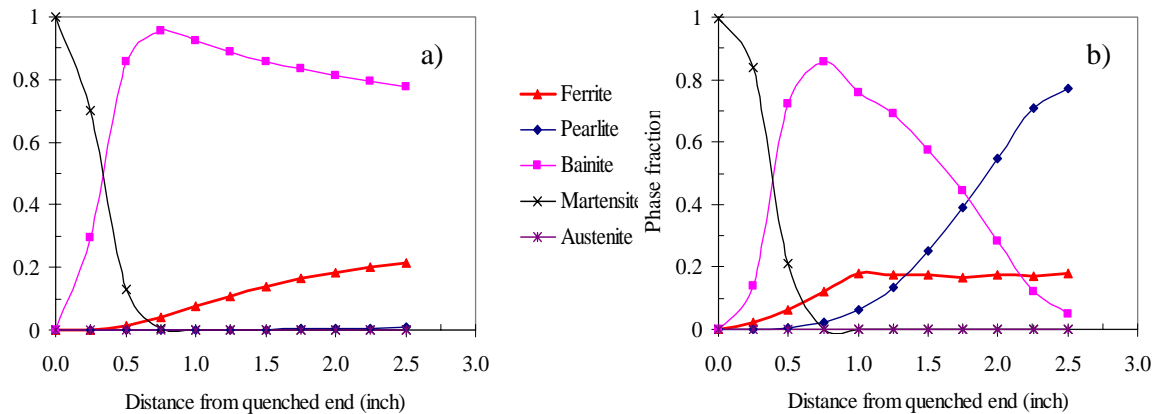


Figure 4. Microstructure change along the Jominy quench bar for a) 4140, and b) 5140 alloys

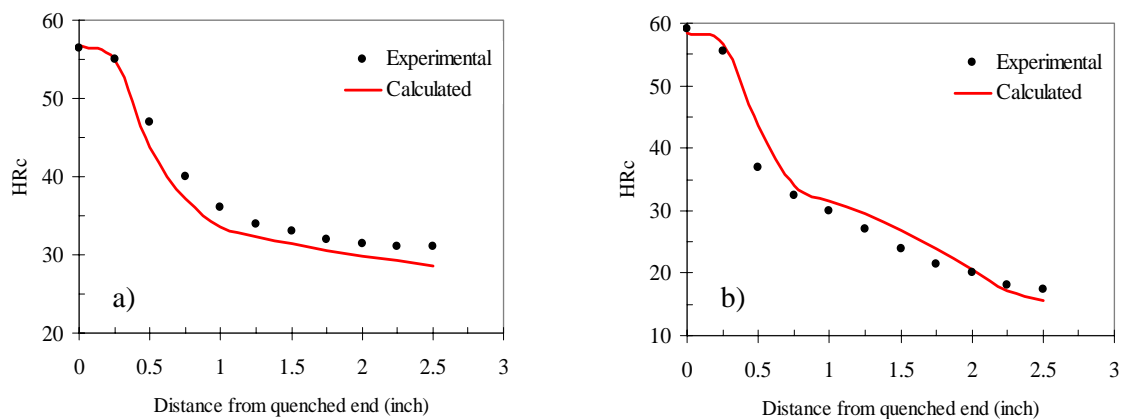


Figure 5. Jominy hardenability comparison between experimental and calculated curves for a) 4140, and b) 5140 alloys

### 3.3 Linking JMatPro with FE/FD-based Deformation Simulation Packages

Material data calculated by JMatPro have been used by users of many FE/FD-based process simulation packages, from MAGMASOFT and PROCAST for casting, DEFORM and FORGE-3D for forging and rolling, to ANSYS which is a general simulation tool. To make JMatPro's data more easily used by process modellers, new subroutines have been created within JMatPro so that the property data is written as files that can be directly used by the simulation packages. Such linking has been successfully developed between JMatPro and the simulation packages mentioned above and is being extended to heat treatment and welding simulation packages. Some examples relevant to deformation/distortion simulation are given below.

Berlin, April 25 – 27, 2007

Figure 6 show TTT curves of the various phases, ferrite, pearlite and bainite using the steel 4140 as an example. For this case, two curves were shown for each transformation, corresponding to 10% and 90%, respectively. Amongst the properties required as input in formulae for determining distortion and deformation are the yield stress and density (inverse of molar volume) of each phase as a function of temperature. Figure 7 shows these properties for each phase during cooling of steel 4140. Similar calculations of flow stress curves as a function of temperature and strain rate are also available.

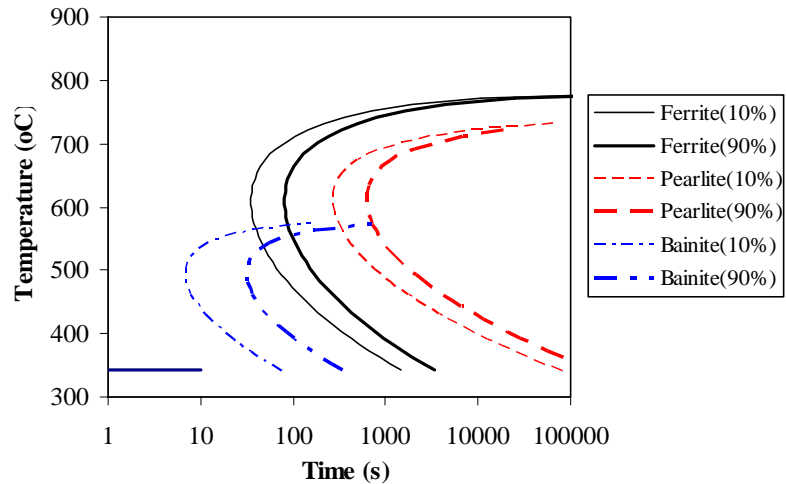


Figure 6. TTT curves of steel 4140, corresponding to 10% and 90% of the transformation.

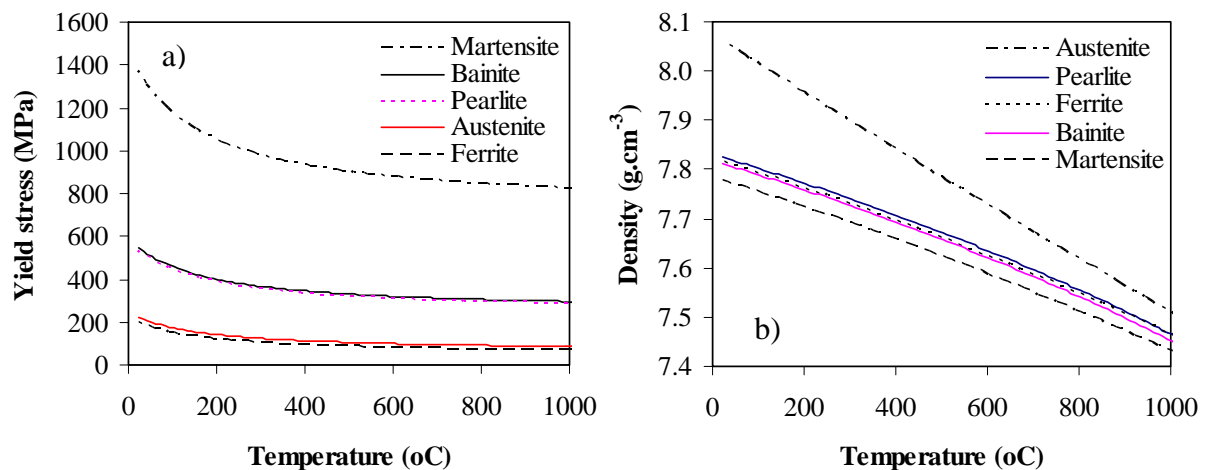


Figure 7. Properties for each phase during cooling of steel 4140, a) yield stress and b) density

## 4 Summary

Properties critical to the prediction of distortion induced by heat-treatment have been calculated using JMatPro, which embodies integrated software for the prediction of both the structure and

Arbeitsgemeinschaft Wärmebehandlung und Werkstofftechnik –AWT

Prof. Dr.-Ing J. Grosch FASM · Chairman 5QCD2007

TU Berlin · FG Werkstofftechnik · EB13· Strasse des 17. Juni 135 · D-10623 Berlin

Phone xx49-30-314-22372· e-mail: [Johann.Grosch@tu-berlin.de](mailto:Johann.Grosch@tu-berlin.de)



**International Federation for Heat Treatment and Surface Engineering – IFHTSE**  
**5th International Conference on Quenching and Control of Distortion**

**A3TS-AWT-ASTT-SVW-VWT**  
**European Conference on Heat Treatment 2007**

**Berlin, April 25 – 27, 2007**

properties of a wide range of alloys. TTT and CCT diagrams, as well as the density and yield stress of key microstructural constituents such as ferrite, pearlite, bainite and martensite for the two steels 4140 and 5140 have been calculated as examples of a larger range of physical, thermophysical and mechanical properties that can be handled in a similar way. Such calculations are available as a function of temperature, including elevated temperatures for which experimental results are often not readily available.

The way that arbitrary cooling profiles can be handled is demonstrated by the calculation of Jominy hardenability profiles which are the result of a complex interplay between thermal and microstructural properties. The variation of properties of different constituents for different cooling rates substantially increase the understanding of the hardness variation along the Jominy bar.

The success of the model is based on accurate description of all the major phase transformations taking place, as well as an accurate calculation of the properties of different phases formed during heat treatment process. The output from JMatPro has already been linked to other FE/FD-based process simulation packages such as MAGMASOFT and PROCAST for casting, DEFORM and FORGE-3D for forging and rolling, and ANSYS which is a general simulation tool. The desired properties could therefore also be linked to any packages that describe the development of the internal stress patterns originating from both elastic and plastic mechanisms.

## References

- ASM (American Society for Metals): Atlas of Isothermal Transformation and Cooling Transformation Diagrams, Metals Park, Ohio, 1977.
- Atkins M.: Atlas of Continuous Cooling Transformation Diagrams for Engineering Steels, Sheffield, British Steel Corporation, 1977.
- Bhadeshia H.K.D.H.: The Driving Force for Martensitic Transformation in Steels, Metal Science, Vol 15, 1981, p.175-177.
- Bhadeshia H.K.D.H.: A Thermodynamic Analysis of Isothermal Transformation Diagrams, Metal Science, Vol 16, 1982, p.159-165.
- Guo Z.; Saunders N.; Miodownik A.P.; Schille J.P.: in 2nd International Conference on Heat Treatment and Surface Engineering in Automotive Applications, 20-22 June, 2005, Riva del Garda, Italy (free download from Ref. [Sente Software 2005])
- Kirkaldy J.S.; Thomson B.A.; Baganis E.A.: Prediction of Multicomponent Equilibrium and Transformation Diagrams for Low Alloy Steels, in Hardenability Concepts with Applications to Steel, eds. Kirkaldy J.S. and Doane D.V., (Warrendale, PA: AIME, 1978), p.82-119.
- Kirkaldy J.S.; Venugopalan D: Prediction of Microstructure and Hardenability in Low Alloy Steels, in Phase Transformations in Ferrous Alloys, eds. Marder A.R. and Goldstein J.I., AIME, (Warrendale, PA: AIME, 1984), p.125-148.
- Lee J.L.; Bhadeshia H.K.D.H.: A Methodology for the Prediction of TTT Diagrams, Materials Science and Engineering A, Vol 171, 1993, p.223-230.

Arbeitsgemeinschaft Wärmebehandlung und Werkstofftechnik –AWT

Prof. Dr.-Ing J. Grosch FASM · Chairman 5QCD2007

TU Berlin · FG Werkstofftechnik · EB13· Strasse des 17. Juni 135 · D-10623 Berlin

Phone xx49-30-314-22372· e-mail: [Johann.Grosch@tu-berlin.de](mailto:Johann.Grosch@tu-berlin.de)



**International Federation for Heat Treatment and Surface Engineering – IFHTSE**  
**5th International Conference on Quenching and Control of Distortion**

**A3TS-AWT-ASTT-SVW-VWT**  
**European Conference on Heat Treatment 2007**

**Berlin, April 25 – 27, 2007**

Li, M.V.; Niebuhr D.V.; Meekjsho L.L.; Atteridge D.G.: A Computational Model for the Prediction of Steel Hardenability, Metall. Mater. Trans., Vol 29B, 1998, p.661-672.

Li, X.; Miodownik, A.P.; Saunders N., Schille J.P.: Transformed -Software simplifies alloy heat treatment, production and design, Materials World, May 2002, p.21-23. (free download from Ref. [Sente Software 2005])

Saunders N.; Guo Z.; Miodownik A.P.; Schille J.P.: The Calculation of TTT and CCT Diagrams for General Steels, Internal report of Sente Software Ltd., Guildford GU2 7YG, U.K. 2004 (free download from Ref. [Sente Software 2005])

Sente Software Ltd.: <http://www.sentesoftware.co.uk/biblio.html> , A collection of free downloadable papers on the development and application of JMatPro, 2005.

Arbeitsgemeinschaft Wärmebehandlung und Werkstofftechnik –AWT

Prof. Dr.-Ing J. Grosch FASM · Chairman 5QCD2007

TU Berlin · FG Werkstofftechnik · EB13· Strasse des 17. Juni 135 · D-10623 Berlin

Phone xx49-30-314-22372· e-mail: [Johann.Grosch@tu-berlin.de](mailto:Johann.Grosch@tu-berlin.de)